

Highly-Bioreactive Silica-Based Mesoporous Bioactive Glasses Enriched with Gallium(III)

Sandra Sánchez-Salcedo^{1,2}, Gianluca Malavasi^{3,*}, Antonio Jesus Salinas^{1,2,*},
Gigliola Lusvardi³, Luca Rigamonti³, Ledi Menabue³ and Maria Vallet-Regi^{1,2}

¹ Dpto. Química en Ciencias Farmacéuticas, Universidad Complutense de Madrid, Instituto de Investigación Sanitaria Hospital, 12 de Octubre, imas12 Madrid, Spain.

² Centro Investigación Biomédica en Red Bioingeniería, Biomateriales y Nanomedicina (CIBER-BBN), Madrid, Spain.

³ Department of Chemical and Geological Sciences, University of Modena and Reggio Emilia, Via G. Campi 103, 41125 Modena, Italy.

* Correspondence: salinas@ucm.es (A. J. Salinas); gmalavasi@unimo.it (G. Malavasi)

Abstract: Beneficial effects in bone cell growth and antibacterial action are currently attributed to Ga³⁺ ions. Thus, they can be used to upgrade mesoporous bioactive glasses (MBGs), investigated for tissue engineering, whenever they released therapeutic amounts of gallium ions to the surrounding medium. Three gallium-enriched MBGs with composition (in mol%) $x\text{SiO}_2-y\text{CaO}-z\text{P}_2\text{O}_5-5\text{Ga}_2\text{O}_3$, being $x = 70, y = 15, z = 10$ for **Ga_1**, $x = 80, y = 12, z = 3$ for **Ga_2** and $x = 80, y = 15, z = 0$ for **Ga_3**, were investigated and compared with the gallium-free $80\text{SiO}_2-15\text{CaO}-5\text{P}_2\text{O}_5$ MBG (**B**). ²⁹Si and ³¹P MAS NMR analyses allow determining that Ga³⁺ acts as network modifier in the glass regions with higher polymerization degree and as network former in the zones with high concentration of classical modifiers (Ca²⁺ ions). **Ga_1** and **Ga_2** exhibited a quick *in vitro* bioactive response because they were coated by an apatite-like layer after 1 and 3 days in simulated body fluid. Although we have not conducted biological tests in this paper (cells or bacteria), **Ga_1** released high but non-cytotoxic amounts of Ga³⁺ ions in Todd Hewitt Broth culture medium that were 140 times higher than the IC90 of *P. aeruginosa* bacteria demonstrating its potential for tissue engineering applications.

Keywords: Gallium ions; mesoporous glasses; glass structure; in vitro bioactivity; antibacterial capability

1. Introduction

The inclusion of so-called therapeutic ions in silica-based mesoporous bioactive glasses (MBGs) is a subject of current interest because of the beneficial effects they can produce once implanted [1]. The advantages given by these ions are connected to that of the traditional components of bioactive glasses: (i) stimulate expression of genes of osteoblastic cells [2], (ii) stimulate angiogenesis [3], (iii) join certain antibiotics to produce antimicrobial behaviour [4] and (iv) show anti-inflammatory effects [5]. In this context, Ga^{3+} ions are being investigated to be included in MBGs to obtain 3D scaffolds for bone regeneration, in particular for the defects treatment due to their propitious effects in bone cell growth and thanks to their antibacterial action. In fact, bone can be considered as target organ for gallium as this metal can be found at sites of rapid bone remodelling, such as active metaphyseal growth plate and healing fractures [6,7]. In 2009, Ma et al reported that gallium improves bone strength and calcium content in osteopenic rats, probably by decreasing the rate of bone resorption [8]. Indeed, gallium was already approved by FDA for the treatment of hypercalcemia and also used for treating Paget's bone disease [9,10]. More recently, gallium has emerged as a new-generation antibacterial ion that may be useful in treating and preventing localized infections. In fact, when Ga^{3+} is exogenously supplied to bacterial cells, it can replace Fe^{3+} perturbing the bacterial metabolism. Therefore, the interest of Ga^{3+} -based antibacterial materials is a complementary strategy for the development of novel drugs to tackle multidrug-resistant bacteria [11–15]. Moreover, in contrast with silver and copper, gallium can be metabolically active by substitution of iron in many biological systems, due to the chemical similarities of Ga^{3+} with Fe^{3+} in terms of charge, ionic radius and electronic configuration [12]. As a result, Ga^{3+} exhibits these positive consequences without inducing cytotoxicity [16].

In MBGs structure, Ga^{3+} ions exhibit an intermediate behaviour between network formers and network modifiers. In a previous paper, MBGs doped with up to 3.5 mol% of Ga_2O_3 were synthesized and characterized [17]. However, these glasses only released imperceptible amounts of Ga^{3+} ions in the medium (below 0.05 ppm in simulated body fluid, SBF), hampering the possible bactericide action of these materials. That study [17] revealed that the release of Ga^{3+} from the final MBG does not depend on the amount added to the glass composition, but on its location in the glass network, which favours or not the liberation in the surrounding medium. Nevertheless, there are several reported examples of gallium-doped glasses, as well as with mesoporous structure [18] and with similar composition to the more soluble phosphate glasses obtained by melting [19], where the high amount of released gallium ions in the physiological medium produced antibacterial effects, even above the biocompatible limit. Taking into account the adequate bioactivity and biocompatible behaviour of MBGs and their high specific surface area to enable the adsorption of therapeutic

molecules and their subsequent release in controlled fashion [12–14], it is of great interest the possibility of releasing a right amount of gallium enough to inhibit the biofilm formation on scaffolds for bone tissue defects.

All these results have highlighted the importance of studying the different positions that can be occupied by gallium ions in the network of a mesoporous glass. Thus, in this paper three mesoporous glasses in the quaternary system $x\text{SiO}_2-y\text{CaO}-z\text{P}_2\text{O}_5-5\text{Ga}_2\text{O}_3$ were synthesized and their chemical structure was investigated by NMR spectroscopy. In particular, the three glasses have the following composition (in mol%): $x = 70, y = 15, z = 10$ for **Ga_1**, $x = 80, y = 12, z = 3$ for **Ga_2** and $x = 80, y = 15, z = 0$ for **Ga_3**, thus containing fixed 5 mol% of Ga_2O_3 and different P_2O_5 contents, 10, 3 and 0 mol%, respectively. These glass compositions were selected searching for glasses able to exhibit different Ga^{3+} release patterns, and they will be compared with the gallium-free $80\text{SiO}_2-15\text{CaO}-5\text{P}_2\text{O}_5$ MBG (**B**). The main objective of this study is the correlation of the location of the gallium ions in the glass network with their bioactive behaviour, and the amount of Ga^{3+} ions released after soaking in common cell culture media, such as Dulbecco's Modified Eagle Medium (DMEM) and Todd Hewitt Broth (THB). Although we have not conducted biological tests in this paper (cells or bacteria), the final goal of this study is to check if these glasses, which maintain a mesoporous structure, are able to exhibit *in vitro* bioactivity as well as to release gallium ions in the bactericide-activity levels but still remaining under the cytotoxic level.

2. Results

2.1 Synthesis of MBGs and their Characterization

The MBGs studied in this paper were obtained by evaporation-induced self-assembly (EISA) process according to a method previously described [17], and their compositions are reported in Table 1. The gallium-containing glass compositions were proposed in order to increase the Ga^{3+} ions released during *in vitro* biocompatibility and antibacterial assays. In particular, in all sample the Ga_2O_3 concentration was raised up to 5 mol% with respect to the amount of 3.5 mol% in the previously reported glass [17]. In **Ga_1** the silica content was reduced while increasing P_2O_5 in order to decrease the polymerization degree of glass network; in fact, it is well known that P_2O_5 is mainly present as orthophosphate unit (Q^0 species) [20]. In **Ga_2** and **Ga_3** we had to reduce progressively the P_2O_5 content, since it was demonstrated that calcium can play a different role depending on bioactive glass composition [21]: in fact, in ternary $\text{SiO}_2-\text{CaO}-\text{P}_2\text{O}_5$ system, Ca^{2+} ions tend to cluster around $[\text{PO}_4]$ orthophosphate units, while Ca^{2+} ions in binary SiO_2-CaO glass break the silica network. These two different structural roles of calcium ions in the ternary and

binary glasses cause a lower amount of released Ca^{2+} ions during bioactivity tests in the first system with respect to the second. In this scenario, Ga^{3+} ions could play a similar role as Ca^{2+} ions, and the lower amount or absence of P_2O_5 in the glass composition could favour the release of Ga^{3+} ions associated to the silica network.

Figure 1 reports low-angle powder X-ray diffraction (PXRD) spectra, which are necessary to verify the possible mesoporous order in **B**, **Ga_1**, **Ga_2** and **Ga_3** after calcination at 700 °C. We can observe that **B** produces a sharp diffraction maximum at 2θ in the region of 1.3–1.4°, assigned to the (10) reflection, along with a less resolved peak at about 2.3° that can be ascribed to the (11) reflection as previously reported [22]. The intensity of the PXRD maxima decreases on passing from **B** to **Ga_2**, indicative of a partial deterioration of the mesoporous order [17]. The **Ga_1** shows a poorly resolved peak in the 1.2–1.4° region hinting for a weaker mesoporous order, while **Ga_3** does not present any diffraction maximum at low angles.

Table 1. Theoretical (and experimental as obtained by EDX analysis) molar percentage (mol%) of the different oxides in prepared mesoporous glasses.

Glasses	SiO_2	CaO	P_2O_5	Ga_2O_3
B	80.0 (82.3)	15.0 (11.6)	5.0 (6.1)	0.0 (0.0)
Ga_1	70.0 (74.0)	15.0 (13.0)	10.0 (7.9)	5.0 (5.1)
Ga_2	80.0 (81.8)	12.0 (10.0)	3.0 (3.2)	5.0 (5.1)
Ga_3	80.0 (80.8)	15.0 (14.2)	0.0 (0.0)	5.0 (5.0)

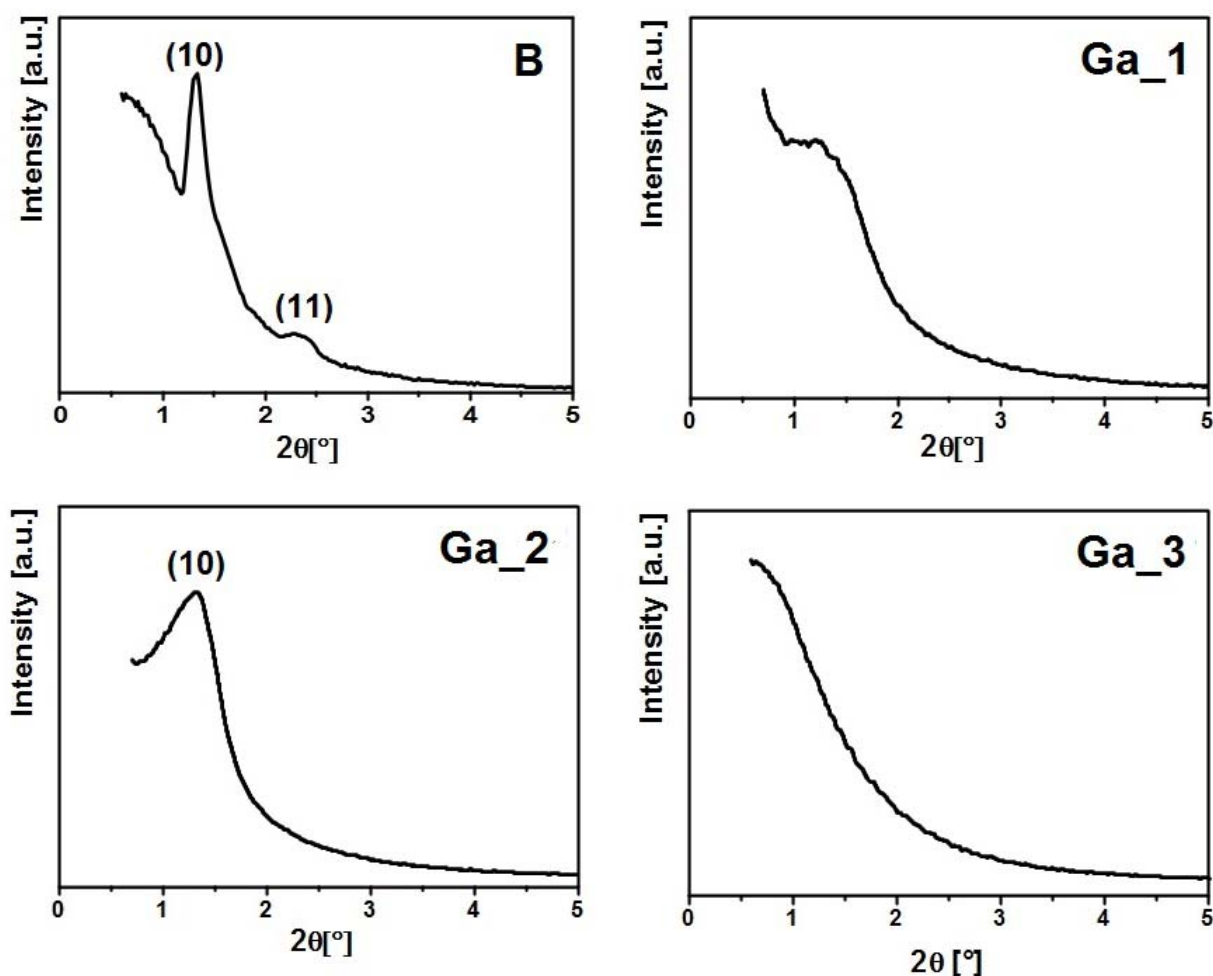


Figure 1. Low-angle PXRD patterns of **B**, **Ga_1**, **Ga_2** and **Ga_3**.

Figure 2 shows the N₂ adsorption-desorption isotherms and the pore size distribution for **B**, **Ga_1**, **Ga_2** and **Ga_3**. The reported isotherms can be classified as type IV, which are characteristic of mesoporous material, and the hysteresis loops are of type H in the mesoporous range, which are distinctive of cylindrical pores. Samples **Ga_1** and **Ga_2** display a single-modal size distribution centred at 2.7 and 3.1 nm, respectively, while **Ga_3** shows two maxima centred at around 3.3 nm and below 1 nm, in which the latter is probably due to microporosity. The pore size distribution is relatively wide, characteristic of mesoporous glasses obtained by EISA method [23]. Textural properties, such as specific surface area (S_{BET}), pore diameter (D_{P}) and total pore volume (V_{P}), of **Ga_1**, **Ga_2** and **Ga_3** are similar to those of gallium-containing mesoporous glasses up to 3.5 mol% of Ga₂O₃ previously reported [17].

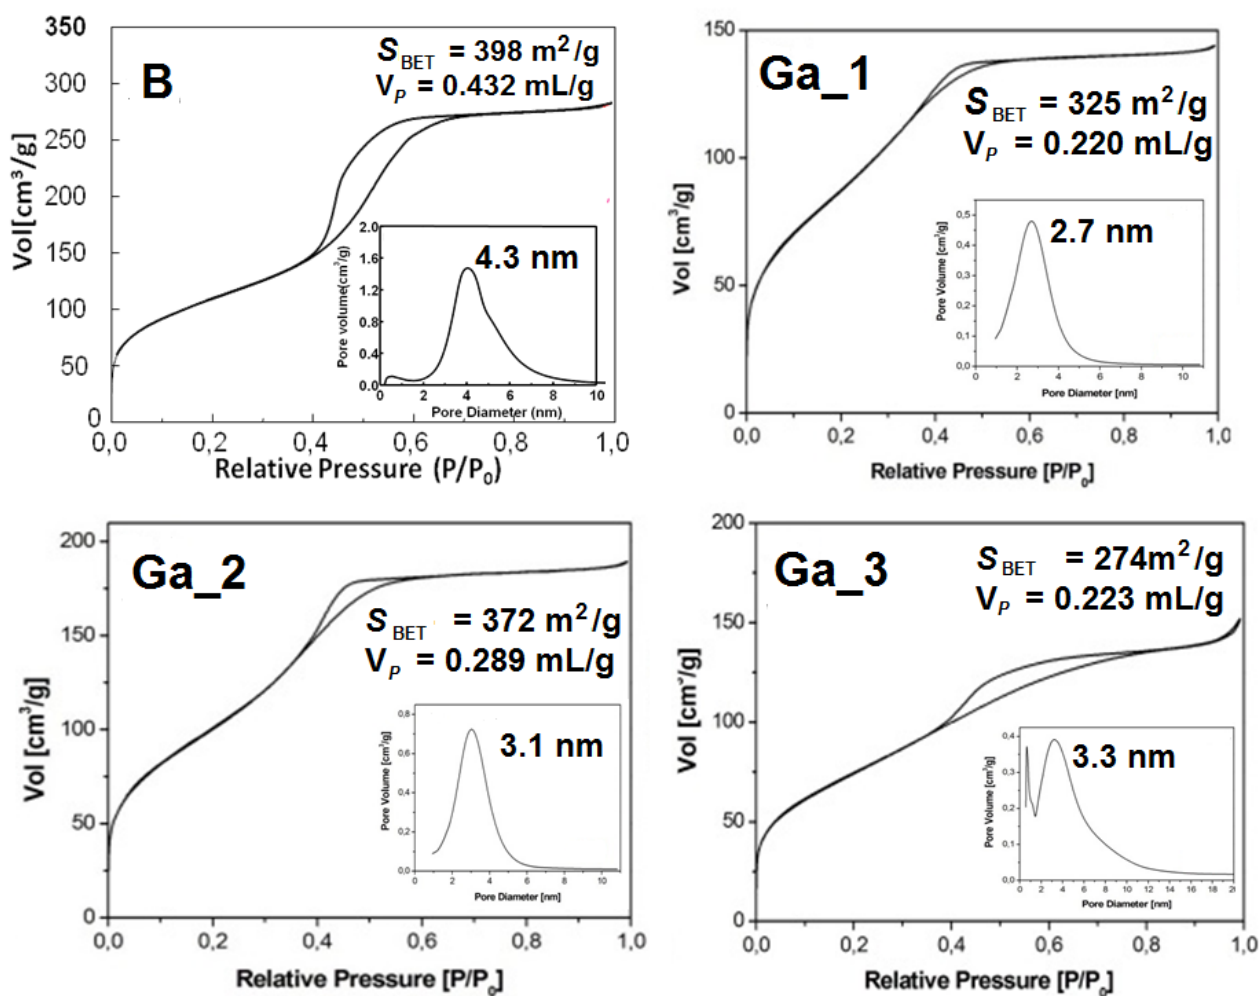


Figure 2. Nitrogen adsorption-desorption isotherms of **B**, **Ga_1**, **Ga_2** and **Ga_3** with reported S_{BET} and V_p values. Insets: pore diameter distribution curves.

Transmission Electron Microscopy (TEM) images of **B**, **Ga_1**, **Ga_2** and **Ga_3** are reported in Figure 3. A typical two-dimensional (2D) hexagonal order mesoporous arrangement channels is shown only by **B**, and this is confirmed by the electronic diffraction shown in the inset. However, also in the images of **Ga_2** it is possible to observe some zones exhibiting mesoporous order. For **Ga_1** and **Ga_3** a poorly ordered structure can be instead recognized. The Energy-Dispersive X-ray (EDX) analysis was also used to determine the experimental composition reported in Table 1 in comparison with the theoretical molar percentages, showing a good resemblance.

^{29}Si and ^{31}P solid-state Magic Angle Spinning (MAS) Nuclear Magnetic Resonance (NMR) measurements were carried out to further investigate the environments of the network-forming species on these samples at the atomic level. Table 2 and Table 3 show the chemical shifts, deconvoluted peak areas, and silica or phosphorous network connectivity (NC) $\langle Q^n \rangle$ for each glass composition. In particular, in Table 2 Q^2 , Q^3 , and Q^4 represent the silicon atoms (denoted Si^*) in

(NBO)₂-Si*-(OSi)₂, (NBO)-Si*-(OSi)₃, and Si*(OSi)₄ (NBO = non-bonding oxygen adjacent to another Si atom), respectively, while in Table 3 Q⁰ and Q¹ represent phosphorus atoms (denoted P*) in the PO₄ units of P*-(NBO)₄ and (NBO)₃-P*-(OP), respectively.

Table 2. Chemical shifts δ (ppm) and relative peak areas (%) obtained by solid-state Single-Pulse and Cross-Polarized ²⁹Si MAS NMR. The areas for Q², Q³ and Q⁴ were calculated by Gaussian line-shape deconvolutions and their relative populations are expressed as percentages; $\langle Q^n \rangle$ represents the silica network connectivity.

²⁹ Si Single-Pulse									
	Q ⁴		Q ³		Q ²		$\langle Q^n \rangle$		
	δ	area	δ	area	δ	area			
B	-111.5	63.4	-101.6	25.0	-91.5	11.6	3.52		
Ga_1	-112.1	45.9	-102.6	48.4	-89.2	5.7	3.40		
Ga_2	-112.0	44.0	-102.0	51.3	-89.0	4.7	3.39		
Ga_3	-112.0	33.2	-102.9	54.8	-89.3	11.9	3.21		

²⁹ Si Cross-Polarization									
	Q ⁴		Q ³		Q ² _H		Q ² _{Ca}		$\langle Q^n \rangle$
	δ	area	δ	area	δ	area	δ	area	
B	-110.4	18.3	-101.2	56.5	-92.4	15.8	-86.3	9.4	2.93
Ga_1	-107.7	20.4	-100.8	37.9	-92.9	19.0	-86.8	22.5	2.78
Ga_2	-106.1	20.2	-101.2	40.6	-92.3	17.6	-84.6	17.6	2.73
Ga_3	-106.8	22.3	-100.9	36.0	-92.7	18.1	-84.0	18.1	2.70

Table 3. Chemical shifts δ (ppm), relative peak areas (%) and phosphorus connectivity, $\langle Q^n \rangle$, obtained by solid-state Single-Pulse ³¹P MAS NMR.

³¹ P Single Pulse					
	Q ⁰		Q ¹		$\langle Q^n \rangle$
	δ	area	δ	area	
B	2.3	94.5	-5.7	5.5	0.06
Ga_1	2.0	93.3	-5.5	6.7	0.07
Ga_2	1.2	90.6	-5.1	9.4	0.09

In the Single-Pulse ²⁹Si MAS NMR spectra, the signals in the region between -111 and -112 ppm come from Q⁴, those from -102 to -103 ppm are given by Q³ and those from -92 to -89 ppm by Q².

Single-Pulse ^{29}Si MAS NMR spectroscopy was used to evaluate the NC of mesoporous glasses as a function of the chemical composition. Sample **B** is characterized by a high percentage of Q^4 and Q^3 species with NC of 3.52, very similar to that found in iso-compositional mesoporous glasses [22]. The introduction of 5 mol% Ga_2O_3 in **Ga_1**, **Ga_2** and **Ga_3** causes a decrease of network connectivity due to the decrease of the percentage of Q^4 and the increase in the amount of Q^3 species. The NC [24] can be also computed using the simplified model proposed by Martin *et al* [25]; using this model the NC value for **B** is 4 assuming that all P is present as orthophosphate units (Q^0). This value is greater than determined by the $\langle\text{Q}^n\rangle$ obtained from Single-Pulse ^{29}Si MAS NMR analysis. This is most likely due to the fact that a fraction of P becomes part of the glass network forming Si–O–P bridges. The model proposed in the aforementioned article can be used to calculate NC for glasses that also contain other forming ions in addition to Si, such as Ga. In fact, if we computed the NC values assuming Si and Ga as network former ions, the results obtained were 4.5, 4.04 and 3.78 for **Ga_1**, **Ga_2** and **Ga_3**, respectively. These values are always greater than found by analysis of the $\langle\text{Q}^n\rangle$, but this can be easily explained by the high amount of OH groups present in the glass network. These groups reduce the connectivity. Moreover, another explanation can be done assuming that not all Ga^{3+} ions play the role of network former.

A similar trend is observed in the Cross Polarized ^{29}Si MAS NMR spectra; however, the network connectivity is lower with respect to that found using the Single-Pulse analysis. The $\langle\text{Q}^n\rangle$ determined by Cross-Polarized MAS NMR spectra is lower than in Single-Pulse experiments, because the first is mainly sensible to the glass surface rich of H nuclei [26].

The Single-Pulse ^{31}P MAS NMR spectra of the materials show a mean maximum in the range of 1–2 ppm, assigned to the Q^0 environment typical of an amorphous orthophosphate. A second weak signal located between –5 and –6 ppm range falls in the range of Q^1 tetrahedra that can be attributed to P–O–Si environments as reported by previous studies [27,28].

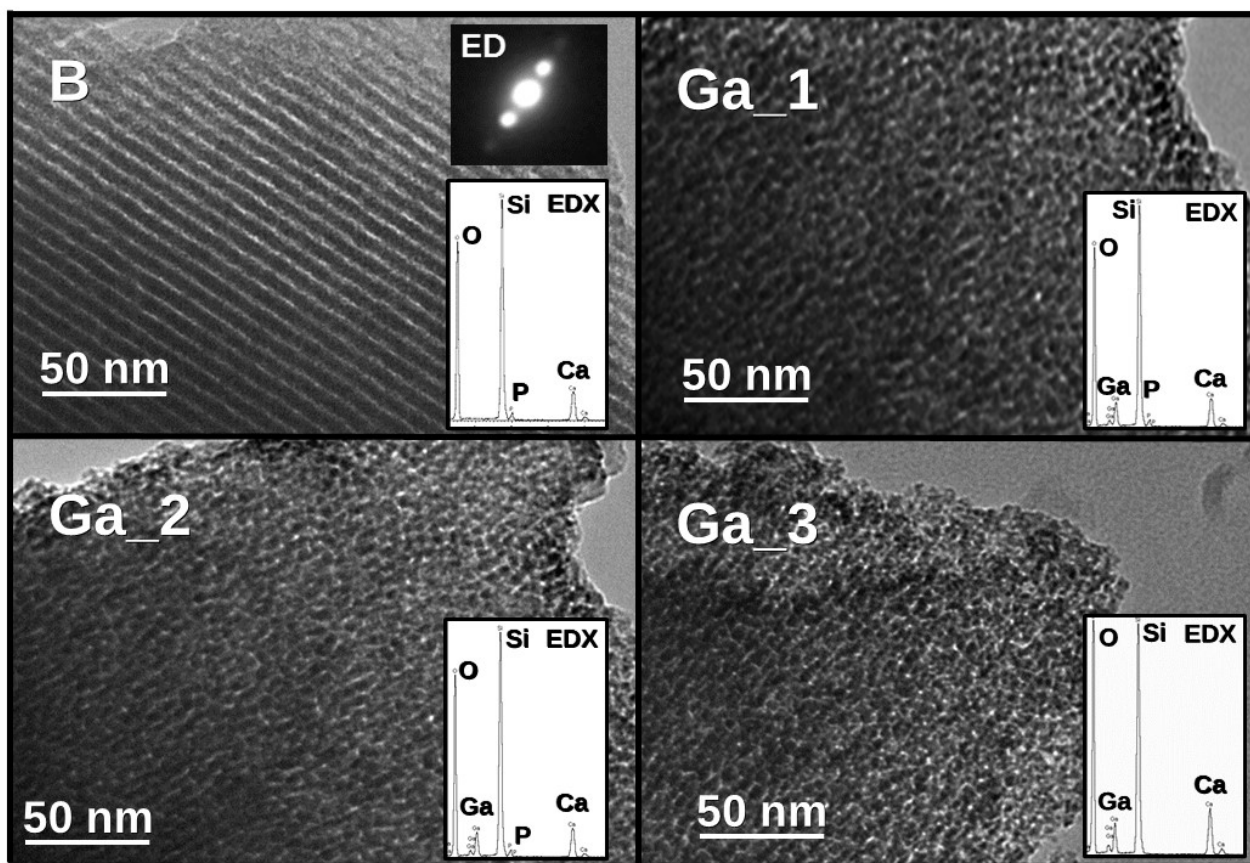


Figure 3. TEM images of **B**, **Ga_1**, **Ga_2** and **Ga_3** with the corresponding EDX spectra included in the downright part of the micrographs. The electron diffraction pattern of **B**, the highest ordered sample, is also included in the upright part of the micrograph.

2.2 *In Vitro* Bioactivity Assay

Figure 4 shows the FTIR spectra of **Ga_1**, **Ga_2** and **Ga_3** before and after being soaked in SBF at 37 °C for 1, 3 and 7 days [29]. The FTIR spectra of all glasses before soaking in SBF show intense absorption bands at 1040 and 470 cm^{-1} that correspond to the asymmetric bending vibrations of the Si–O–Si bond, and a band at 800 cm^{-1} , attributable to symmetric stretching of the Si–O bond [30]. The weak band at 585 cm^{-1} present in **Ga_1** and **Ga_2** was ascribed to phosphate group in amorphous fashion, while **Ga_3** present a band at 605 cm^{-1} , attributed to the Ga–O in tetrahedral coordination [31].

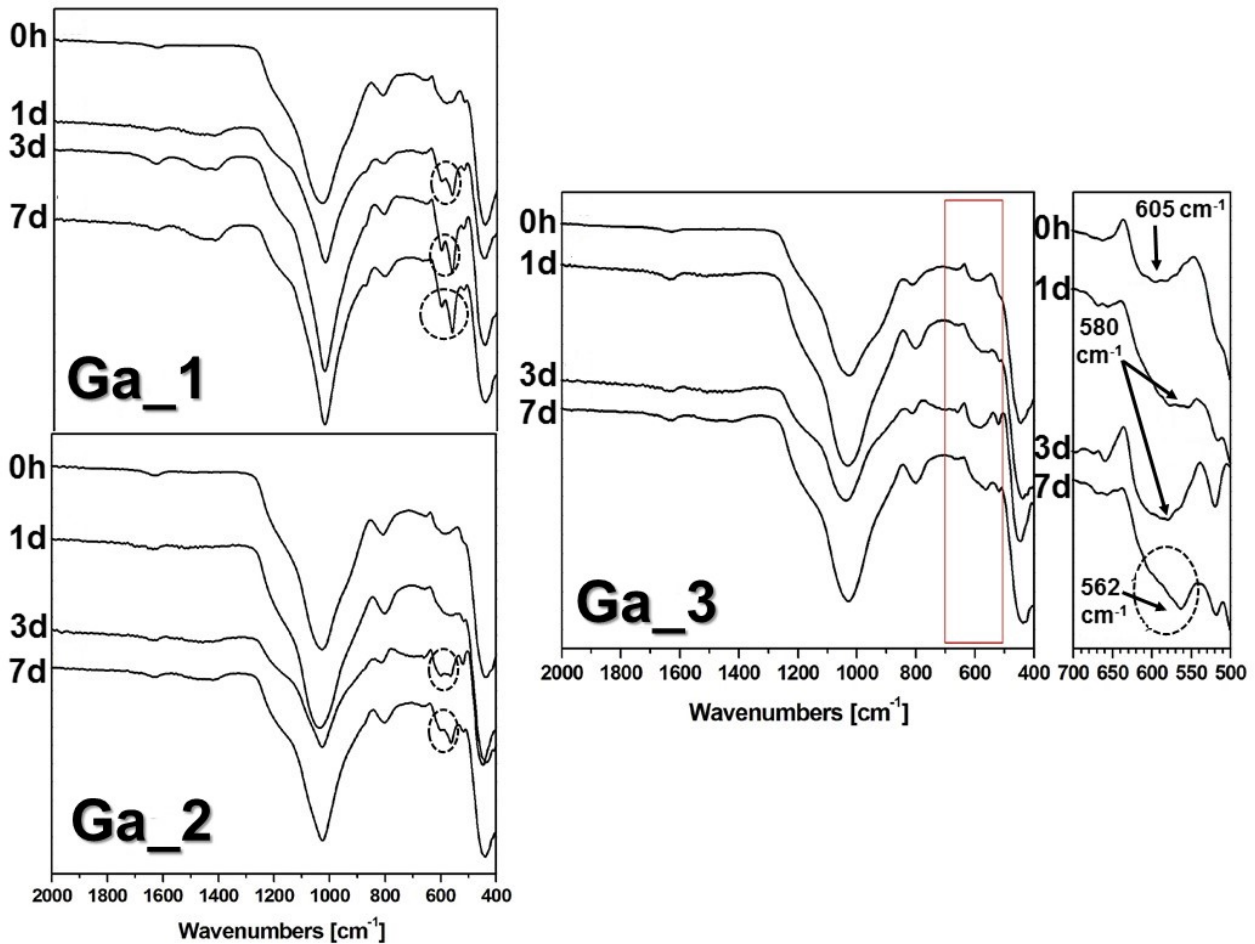


Figure 4. FTIR spectra of **Ga_1**, **Ga_2** and **Ga_3** before (0 h) and after (1 d, 3 d and 7 d) soaking in SBF. Circles show the formation of P–O doublet assigned to crystalline calcium phosphate.

Different types of *in vitro* responses can be recognized for the different samples. In particular, a high *in vitro* bioactivity was shown by **Ga_1** comparable to that found for **B** [17] (not reported in the present study for the sake of brevity). In fact, already after 1 day of soaking in SBF it was possible to observe the formation of the characteristic doublet at 564 and 602 cm^{-1} , usually assigned to crystalline calcium phosphate [32]. Sample **Ga_2** showed an intermediate behaviour, since the doublet at 564 and 603 cm^{-1} appeared after 7 days of soaking in SBF (see Figure 4), while lower *in vitro* bioactivity was given by **Ga_3** because after 1 day of soaking the formation of a broad peak centred at 580 cm^{-1} (inset in Figure 4) due to the formation of amorphous Ca–P layer could be observed. At longer times no peak attributed to the crystallization of calcium phosphate appeared, and only a shoulder at 562 cm^{-1} became visible.

The bioactivity in terms of apatite-like layer (for example hydroxycarbonate apatite, HCA) formation after different times of soaking in SBF is reported as PXRD spectra in Figure 5. The peaks at about 32° and 26° in 2θ are attributed to the (211) and (002) reflections of hydroxyapatite (JCPDS-PDF 74-0565). Increasing the soaking time, more diffraction peaks due to hydroxyapatite

become evident for **Ga_1**, suggesting the crystallization of the phase. After 7 days of soaking the (211) reflection of hydroxyapatite appeared only for **Ga_2**, while for **Ga_3** the PXRD spectrum showed only the broad band centred at 22–23° in 2θ characteristic of amorphous silica. Hence, the PXRD results confirm the trend observed in FTIR analysis.

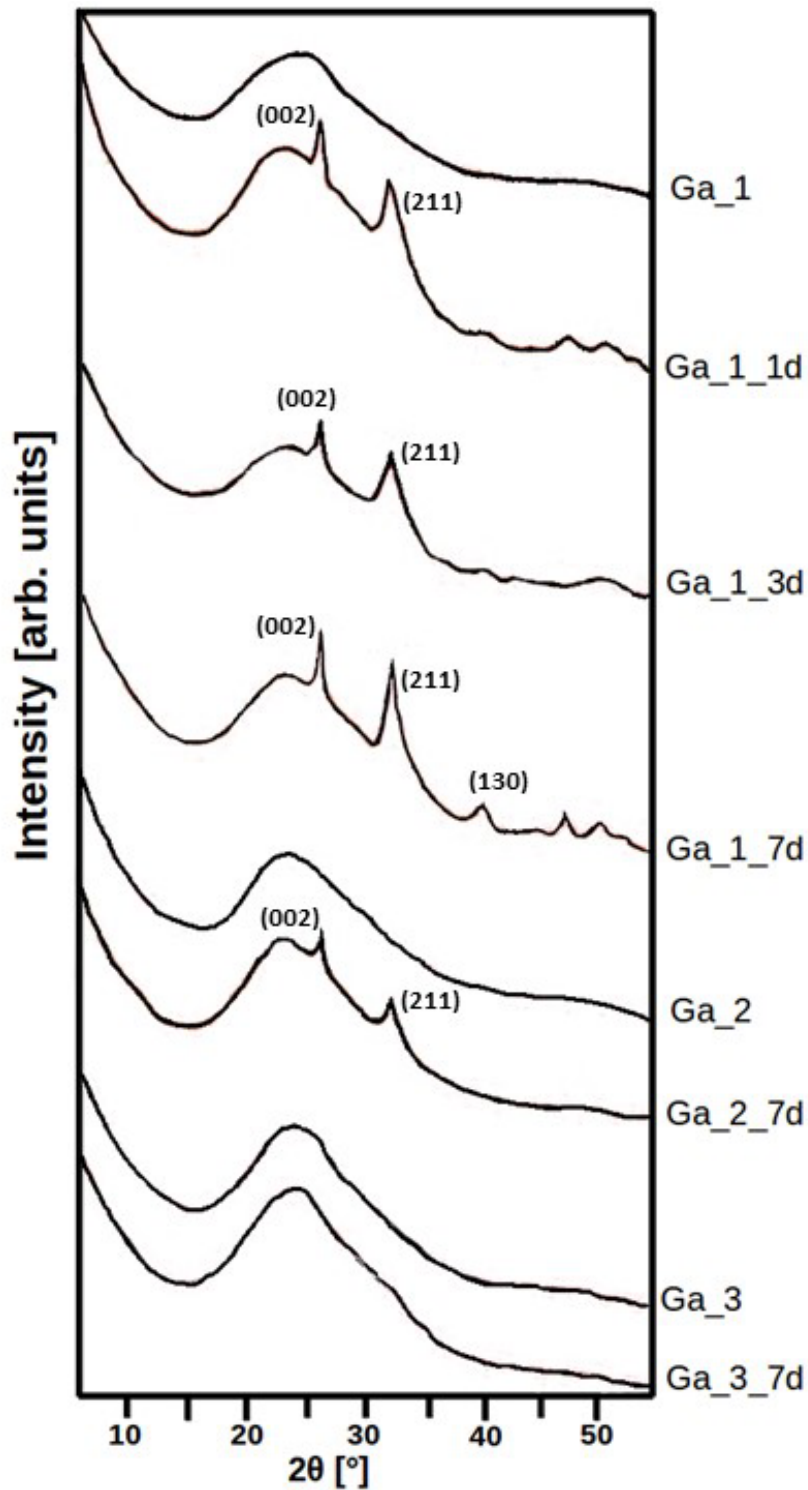


Figure 5. PXRD patterns of **Ga_1**, **Ga_2** and **Ga_3** after different times of soaking in SBF.

Figure 6 shows the Scanning Electron Microscopy (SEM) micrographs and EDX analyses on pellets of **Ga_1**, **Ga_2** and **Ga_3** after 7 days of soaking in SBF. The **Ga_1** surface (Figure 6a) was covered by a thick layer of flake-like particles rich in Ca and P with a Ca/P ratio of 1.48. A similar result can be observed for **Ga_2** (Figure 6b), however the glass surface seems less homogeneous and the Ca/P ratio is 1.43. The morphology of the surface and the Ca/P ratio of **Ga_3** are instead significantly different from the previous samples (Figure 6c). These results agree with those observed by FTIR and XRD.

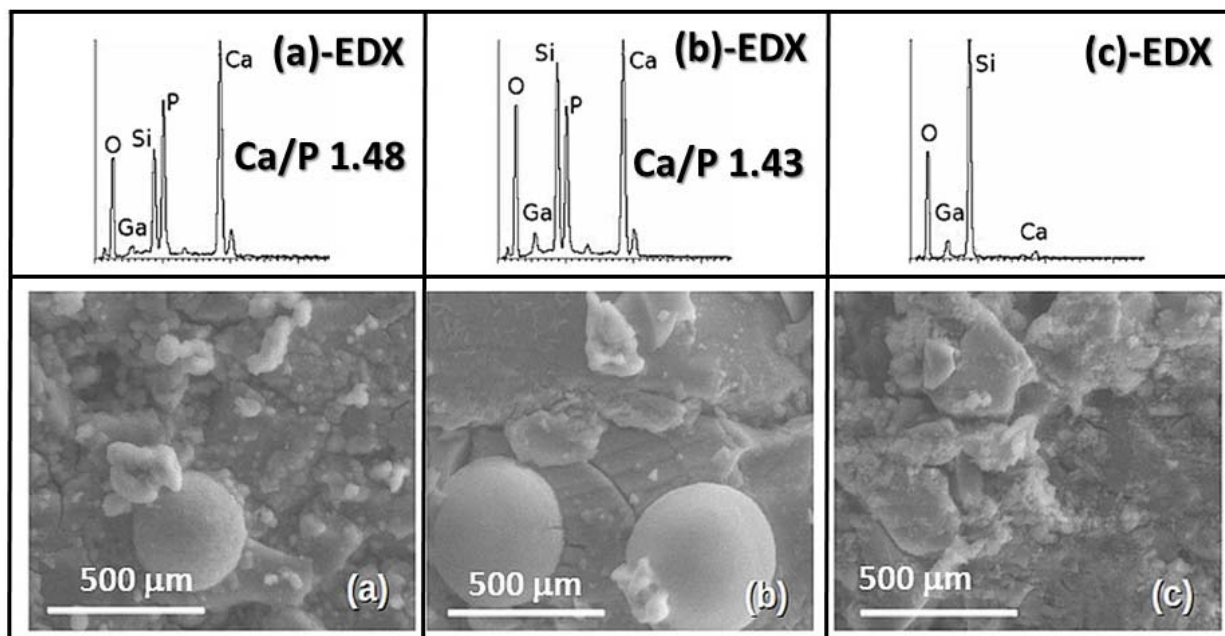


Figure 6. SEM micrographs and EDX analyses of (a) **Ga_1**, (b) **Ga_2** and (c) **Ga_3** after 7 days of soaking in SBF.

2.3 Ion Release Tests

Changes in the SBF concentration during *in vitro* bioactivity tests can be used as an indirect method for understanding the process occurring on the glass surface. In fact, bioactive glasses are partially soluble; as a general requisite for bioactivity, an initial increase in Ca, P and Si ions in solution has to take place. After this, Ca and P concentrations in solution decrease suggesting the formation of calcium phosphate layer. The above events could be observed (see Figure 7) for **Ga_1** and **Ga_2**, while for **Ga_3** the concentration of Ca^{2+} ions increased till 7 days and the phosphorus concentration slightly decreased. Moreover, it is interesting to note that the maximum release of Ga^{3+} was observed after 72 h for **Ga_1**, while at longer times the concentration decreased, suggesting a partial precipitation of gallium-containing compounds.

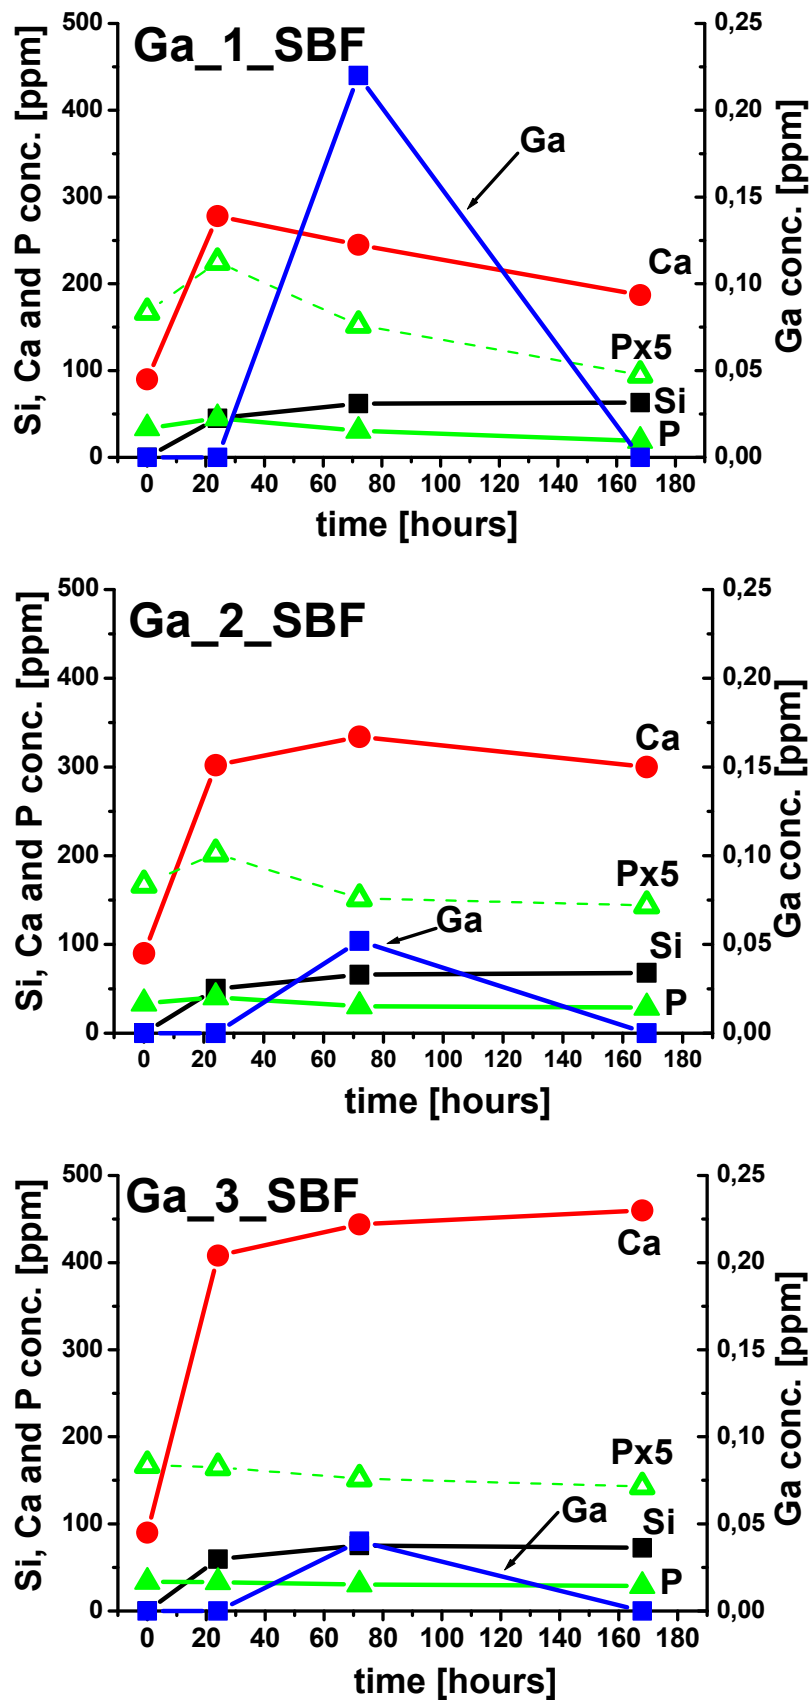


Figure 7. Evolution of calcium, phosphorus, silicon and gallium concentrations with time (P×5 represents phosphorus content magnified by a factor five for better viewing) after soaking of **Ga_1**, **Ga_2** and **Ga_3** in SBF medium.

To verify the simultaneous cyto-compatibility and antibacterial capacity, the cumulative release of Ga was determined and it is reported in Figure 8. Sample Ga_1 showed the maximum release of Ga³⁺ ions both in DMEM and THB, with the highest concentration in DMEM of about 2.5 ppm.

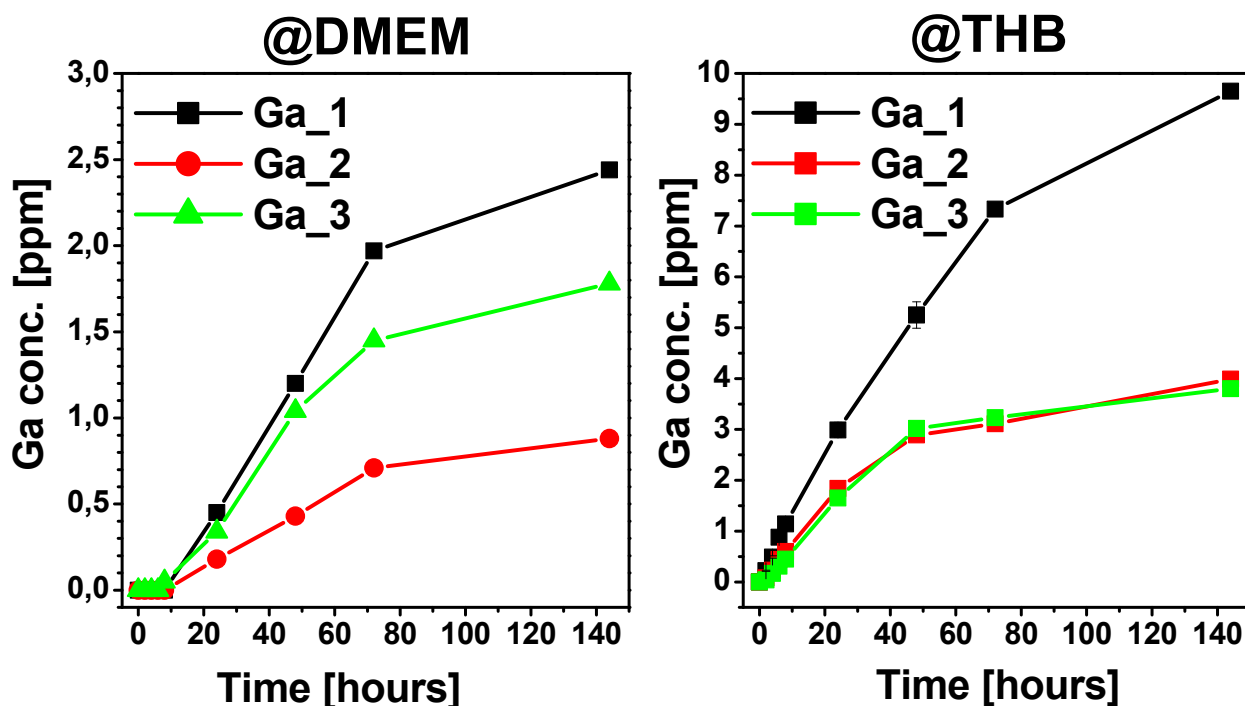


Figure 8. Evolution of Ga³⁺ ions release for Ga_1, Ga_2 and Ga_3 after soaking in DMEM and THB media.

3. Discussion

The material characterization (PXRD, TEM and N₂ adsorption) indicates that **B** (without Ga₂O₃) presents a 2D hexagonal meso-structure (plane group p6mm), while the introduction of Ga₂O₃ decreases this ordered phase. As reported in the previous study [17], the addition of Ga₂O₃ up to 3.5 mol% caused the decrement of mesoporous order and of S_{BET} , D_P and V_P with respect to the mesoporous glass without Ga₂O₃, while the increment of Ga₂O₃ from 3.5 to 5 mol% of the present study seems not to affect the textural properties, which remains good enough to be used in bone tissue engineering.

The MAS NMR analyses performed on the samples helped us to obtain information of the medium-range glass structure. On the basis of previous studies, Ga³⁺ ions are classified as intermediate glass network, however they could also act as network former and modifier as a function of glass composition [33,34]. The ions classified in this way often act as network former in glass with a high

percentage of alkali and alkali-earth oxides in the composition, while they act as network modifier in glass with a high % of SiO₂.

In our gallium-containing glass systems, the Ga³⁺ ions cannot be classified as only former ions, as highlighted by comparing our Single-Pulse ²⁹Si MAS NMR analysis and the NC values computed using Si and Ga as former ions [25]. The effect of Ga₂O₃ on the ²⁹Si Single-Pulse MAS NMR data reported in Table 2 can be explained considering that, when Ga³⁺ is included in the high polymerized silica glassy matrix, these ions actuate the network modification with increased intensity of Q³ signal. In fact the signal attributed to Q³ units shift from -101.6 ppm for **B** to around -102.6 ppm for gallium-containing glasses, suggesting that both Ca²⁺ and Ga³⁺ ions interact with the NBOs of the units. In particular, their formation is maximum for **Ga_3**, and this is probably due to the absence of P₂O₅ in the glass composition. In ³¹P MAS NMR spectra, signals due to orthophosphate Q⁰ units appeared, and these units need positive ions (i.e. Ca²⁺ and Ga³⁺) to compensate their negative charge, so in **Ga_1** and **Ga_2** Ga³⁺ ions act also as charge compensator of PO₄³⁻ units causing a lower amount of gallium in the silica matrix.

Regarding Q², this signal decreases in **Ga_1** and **Ga_2** with respect to **B**, which is indicative that Ga³⁺ behaves also as network former in the structure of these samples, favouring the conversion of Q² into Q³ species. In fact, the intermediate role of Ga³⁺ ions is well known: they play a network modifier role in the zone with a high degree of polymerization, while they act as network former in the zone with a high concentration of classical modifier (such as Ca²⁺ ions) with a consequent low degree of polymerization. This finding is in agreement with the increment of polymerization degree (<Qⁿ>) found by classical molecular dynamic simulations performed on bioactive glasses based on the 45S5 Bioglass® composition modified by the addition of 1 mol% Ga₂O₃. In fact, this glass system presents a high percentage of classical modifiers (Ca²⁺ and Na⁺ ions) and the Ga³⁺ ions play the role of former ions causing an enhancement of <Qⁿ> value [35].

The connectivity determined by Cross-Polarized MAS NMR spectra is lower than in Single-Pulse experiments, because the first technique is mainly sensible to the glass surface rich of H nuclei [26]. In particular, as previously observed [27], it is possible to distinguish two types of Q² units (Table 2): (i) Q²_H with the signal between -92 and -93 ppm and (ii) Q²_{Ca} with the signal between -84 and -86 ppm.

The shifted Q⁴ signals in Cross-Polarized spectra slightly increase in all cases (less negative) with respect to **B**, i.e. when gallium is included, because this ion behaves as weak network former [36]. The role of weak network former attributed to Ga³⁺ ions could be explained by the formation of units signed as Ga former on the glass surface, as shown in Figure 9. This finding is in full agreement with a previous study on similar sol-gel glasses [34] where the Ga³⁺ ions on the surface can act both as network former and modifier (Figure 9) [37]. In particular, the picture reported in

the right side of Figure 9 shows coordinatively unsaturated Ga^{3+} ions acting as modifier ions on the glassy surface; these species present on the material surface are known as *cus* (cation unsaturated species) [38].

The percentage of Ga acting as network former is a minority, while most of the metal ions behave as network modifier. In fact, from data of Table 2, it is possible to see that the percentage of Q^2 species grows significantly for gallium-containing glass with respect to **B**. Therefore, we can conclude that Ga^{3+} ions in the glass surface mainly act as network modifier ions. Interesting to note that the maximum increment of Q^2 species was detected for **Ga_1** (22.5%), which suggests that the higher amount of Ga^{3+} ions in this glass behave as network modifiers with respect to the others gallium-containing glasses.

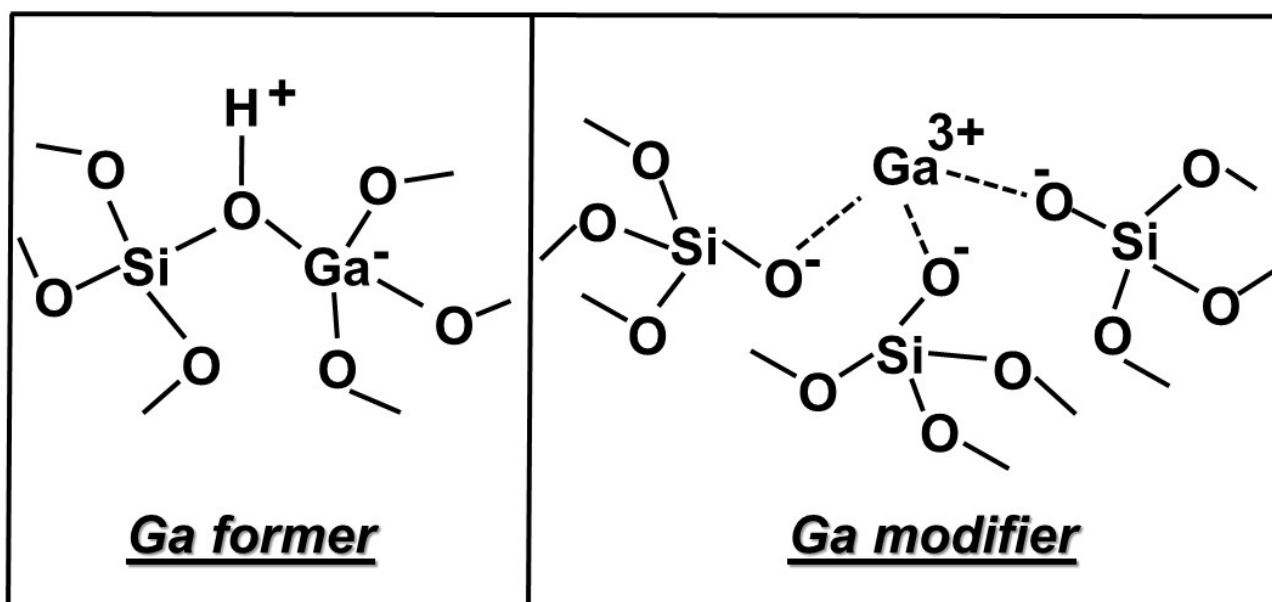


Figure 9. Ga^{3+} ion acting as network former (left) and as network modifier (right) on an MBG surface network.

Phosphorous is mainly present as orthophosphate units; however, it is interesting to note that the introduction of gallium causes a slight increase in the percentage of Q^1 units. However, they could be given by the formation of P-O-Ga , in accordance with the chemical shift determined by Ren and Eckert [39]. This trend is in line with the intermediate role of gallium: in fact, Linati *et al* [40] find a similar trend studying the effect of intermediate zinc ions in bioactive glasses where a shift towards lower ppm's in ^{31}P MAS NMR was detected by the increase of the percentage of ZnO in the glass [22]. The formation of P-O-Ga bridges was also detected in medium range analysis performed using classical molecular dynamic simulations performed on bioactive glasses based on the 45S5 Bioglass® composition modified by the addition of Ga_2O_3 [35].

The network connectivity derived from MAS NMR analysis can be used to explain the different behaviour of the samples toward the bioactivity determined by FTIR and PXRD analyses. In case of **Ga_1** and **Ga_2** the network connectivity is similar in both Single-Pulse and Cross-Polarized ^{29}Si MAS NMR spectra, but Q^1 signal as determined by ^{31}P MAS NMR is smaller in **Ga_2** in spite of a higher P_2O_5 % in **Ga_1**. This would indicate the presence of Ca- and P-clustered zones that are reported to favour the conversion of amorphous calcium phosphate into hydroxyapatite [20].

However, **Ga_3** shows lower network connectivity but conversely it does not exhibit HCA formation: this is probably due to its phosphorous-free composition. In fact, the behaviour of glasses seems strictly related to the amount of P_2O_5 present in the glass composition: in particular the absence of P_2O_5 in **Ga_3** avoids the presence of Ca- and P-clustered zones.

The release of Ca and Ga seems to be related to the P_2O_5 content. The glass with lower P_2O_5 mol% releases Ca^{2+} ions faster and this can be explained by the formation of Ca–P rich zones insoluble in aqueous moiety. The effect of P_2O_5 mol% in the glass composition on Ga release after 3 days is opposite with respect to Ca release: in fact **Ga_1** shows the highest P_2O_5 content. The interpretation of this behaviour is more complicated and this cannot be explained only by taking into account the phosphate content.

In fact, as reported in the previous Cross-Polarized ^{29}Si MAS NMR section, in **Ga_1** the Ga^{3+} ions on the surface act mainly as network modifier bringing to a maximum amount of Q^2_{Ca} species (22.5%). These species possess the lowest polymerization degree on the surface and this explains the highest Ga release. Moreover, in order to explain the highest Ga^{3+} ions released by **Ga_1**, we can suppose a higher concentration of Ga on the glass surface with respect to the bulk with a low polymerization degree, and this enrichment was previously confirmed by XPS analysis [34].

It is very interesting to consider that, in a previous paper, we reported that in ternary CaO– P_2O_5 – SiO_2 sol-gel glasses inclusion of 10% of P_2O_5 avoided the *in vitro* bioactive response in SBF [21]. Indeed, to the best of our knowledge, no MGBs containing a percentage of P_2O_5 as high as 10%, together with a 5% of Ga_2O_3 in its composition, were reported until now. Thus, it is surprising the high *in vitro* bioactive response exhibited by **Ga_1**, which contains just 10% of P_2O_5 . In the mentioned paper [21], we demonstrated that a relatively smaller amount of P_2O_5 , close to 5%, was beneficial for the glasses bioactivity. The reason is that P_2O_5 binds to calcium forming calcium phosphate nuclei, which favour the formation of an HCA layer in SBF, characteristic of materials exhibiting *in vitro* bioactivity [41].

Indeed, the smaller amounts of P_2O_5 allow the presence of enough Ca^{2+} ions in the glass network able to be released in the surrounding medium. This process increases the super-saturation with respect to the apatite and, simultaneously, provokes the formation of new surface silanol groups (Si-OH), and both factors favour HCA deposition. On the other hand, the presence of higher

amounts of P_2O_5 binds all the Ca^{2+} ions of the glass avoiding its release, with the subsequent elimination of the bioactive response of the glass.

Nevertheless, **Ga_1** exhibits another non-favourable characteristic for bioactivity, i.e. the presence of Ga^{3+} ions. Indeed, we reported that the additions of up to 3.5% of Ga_2O_3 in mesoporous glasses decrease the kinetic of the bioactive response [20]. However, in this sample the simultaneous inclusion of high amounts of both elements (P and Ga) produces instead a remarkable increase in the *in vitro* bioactivity. This could be explained taking into account that Ga^{3+} ions could bind to phosphate groups making easier the release of Ca^{2+} ions into the solution. In the present study we could find a glass composition (**Ga_1**) able to release a higher amount of Ga^{3+} ions in solution with respect to previous Ga-MBG samples with a maximum amounts of 3.5% of Ga_2O_3 (for example 0.22 ppm vs. < 0.05 ppm) with a faster *in vitro* bioactivity response if compared with previous Ga-MBG samples [17].

The cumulative gallium release in SBF is lower than reported for the toxicity limit in blood plasma (14 ppm) [11], while in THB was around 9.8 ppm ($\approx 140 \mu M$), 140 times higher than IC90 of *Psuedomonas aeruginosa* and only twice lower than the IC90 of *S. aureus* [42]. In view of these results, the most interesting MBG investigated for bone regeneration is **Ga_1**. In fact, this mesoporous glass presents the fastest *in vitro* bioactive response and potential antibacterial activity.

4. Materials and Methods

4.1 MBG Preparation

MBGs **B**, **Ga_1**, **Ga_2** and **Ga_3** were obtained by EISA process using Pluronic® P123 surfactant (P123, Sigma Aldrich). Tetraethylorthosilicate (TEOS), triethylphosphate (TEP), calcium nitrate tetrahydrate and gallium nitrate monohydrate (SigmaAldrich) were used as source of SiO_2 , CaO , P_2O_5 and Ga_2O_3 , respectively. These reactants were added in the desired ratio to a solution of P123 (4.5 g) and HNO_3 0.5 N (1.12 mL) in ethanol (85 mL). The sol was cast in Petri dish followed by gelation, ageing and drying at room temperature for 7 days. The dried gel was calcined at 700 °C for 3 h to remove surfactant and then subjected to milling and sieving to obtain grains under 32 μm for the pellets preparation.

4.2 MBG Characterization

PXRD experiments were performed with a Philips X'Pert diffractometer equipped with $Cu-K\alpha$ radiation (wavelength 1.5418 Å). PXRD patterns were collected in the 2θ range between 0.6 and 8°

with a step size of 0.02° and counting time of 5 s per step.

EDX analysis was performed with a JEOL 6400 microscope to study the amount of silicon, calcium, phosphorus and gallium and determine the experimental glass composition (Table 1).

Nitrogen adsorption – desorption at 77.35 K was used to determine the textural properties using a Micromeritics ASAP 2020 porosimeter. Before adsorption measurement, the samples were degassed under vacuum for 24 h at 120°C . The surface area was obtained by applying the Brunauer-Emmett-Teller (BET) method [43]. The pore size distribution was determined by the Barret-Joyner-Halenda (BJH) method [44] from the desorption branch of the isotherm.

TEM and electron diffraction were carried out in JEOL 2000FX microscope operating at 200 kV.

Solid-state Single-Pulse MAS NMR spectra were recorded on a Bruker AV-400-WB spectrometer (Karlsruhe, Germany). Samples were spun at 10 kHz for ^{29}Si and 6 kHz in the case of ^{31}P . Spectrometer frequencies were set to 79.49 and 161.97 MHz for ^{29}Si and ^{31}P , respectively. Chemical shift values were referenced to tetramethylsilane (TMS) and H_3PO_4 for ^{29}Si and ^{31}P , respectively. The spectra were obtained also using a proton enhanced Cross-Polarized method, using a contact time of 1 ms. The time period between successive accumulations was 5 and 4 s for ^{29}Si and ^{31}P , respectively, and the number of scans was 10.000 for all the spectra.

4.3 *In Vitro* Bioactivity Tests

After calcination, glasses were ground and sieved to obtain grains with diameter lower than $32\ \mu\text{m}$. The bioactivity tests were performed putting 50 mg of each sample in PE bottle and soaking in 10 mL of SBF [29]. The SBF solution was previously filtered with a $0.22\ \mu\text{m}$ Millipore system to avoid bacterial contamination. Each sample was soaked for three different time intervals (1, 3 and 7 days) in SBF at 37°C under continuous orbital stirring (120 rpm). After soaking, the solutions were taken out by aspiration and filtered, while the powders were gently rinsed first in distilled water and then in ethanol. Later they were dried in a laminar airflow for 24 h. The chemical composition of the remaining solutions was analysed using an ICP spectrometer (ICP Optima 4200DV, Perkin Elmer) to evaluate the changes in the concentration of calcium, silicon, phosphorus and gallium during the *in vitro* bioactivity tests.

Characterization of the powders surface after *in vitro* bioactivity test was performed by FTIR analysis with a Nicolet Magna IR 550 spectrometer using ATR setup. SEM analysis was also carried out in a JEOL 6400 microscope and a JEOL 6335F to study the morphology of surface of the samples. EDX analysis was performed with a JEOL 6400 microscope to evaluate the amount of silicon, calcium, phosphorus, and gallium after *in vitro* analysis.

PXRD patterns in the 2θ range between 5 and 55° with a step size of 0.02° and counting time of 5 s

per step were collected on the sample surface after SBF soaking to determine the crystal phase formed.

We performed also SBF test using 50 mg of powders of each samples compacted into pellets of 6 mm in diameter and 2 mm in thickness. These pellets were suspended in 10 mL of SBF and after 7 days the surfaces were analysed with SEM to study the morphology of the samples and with EDX experiments to determine the compositional variations and the Ca/P ratio.

4.4 Ion Release Tests

In order to simulate the bacteria and cellular tests, as reported in ref. 22, 50 mg of powders of each sample were compacted into pellets of 6 mm in diameter and 2 mm in thickness. The tests were carried out by putting the pellet in a glass container and soaked in 2 mL of DMEM or THB and then placed in a 37 °C incubator under continuous orbital stirring (120 rpm). At various time points (2, 4, 6, 8 h and 1, 2, 3 and 7 days), the pellets were taken out of their respective containers. The solutions were analysed using ICP spectrometry (ICP Optima 4200DV, Perkin Elmer) to evaluate the changes in the concentration of gallium, silicon, calcium and phosphorus. All the pellets were placed into 2 mL of a fresh DMEM or THB solution and this operation was performed until the last time point (7 days). This procedure allowed determining the cumulative ion release curves showed and discussed in the result section.

5. Conclusions

Three MBGs containing 5% of Ga₂O₃ were investigated and compared with an analogous gallium-free glass used as reference. They exhibit mesoporous structure and high S_{BET} surface areas (274–372 m² g⁻¹). NMR analysis allowed determining the location of Ga³⁺ ions in the glass network and to relate this position with the *in vitro* bioactivity and the proportion of Ga³⁺ ions released after soaking in physiological solutions. **Ga_1** was coated by an apatite-like layer after only 1 day in SBF, being the first time that an MBG containing a percentage of P₂O₅ as high as 10% and of Ga₂O₃ as high as 5% shows such a high bioactive response. This behaviour is attributed to the higher amount of modifier ions (Ca²⁺ and Ga³⁺) and consequently a higher depolymerized network. On the other hand, **Ga_2** required 3 days and **Ga_3** was not coated by HCA even after 7 days of soaking. In addition, **Ga_1** was able to release relatively high amounts of Ga³⁺ ions when in contact with *in vitro* solutions (DMEM and THB). The Ga concentration released from **Ga_1** is inside the non-cytotoxic level reported in the literature as well as in the range of efficacy against *P. aeruginosa* bacteria and not far from the effective range reported against *S. Aureus*. Thus, **Ga_1** is the first Ga-

substituted MBG able to exhibit both quick *in vitro* bioactivity and potential antibacterial properties with non-cytotoxic effect.

Acknowledgements: This study was supported by research grants from Instituto de Salud Carlos III (PI15/00978) project co-financed with the European Union FEDER funds, the European Research Council (ERC-2015-AdG) Advanced Grant Verdi-Proposal No.694160 and MINECO MAT2015-64831-R project, and the University of Modena and Reggio Emilia, through the financial support “Progetto Mobilità Internazionale”.

Conflicts of Interest: The authors declare no conflict of interest.

References

1. Wu, C.; Chang, J. Multifunctional mesoporous bioactive glasses for effective delivery of therapeutic ions and drug/growth factors. *J. Control. Release* **2014**, *193*, 282–295, doi: 10.1016/j.jconrel.2014.04.026.
2. Xynos, I.D.; Edgar, A.J.; Buttery, L.D.K.; Hench, L.L.; Polak, J.M. Gene-expression profiling of human osteoblasts following treatment with the ionic products of Bioglass[®] 45S5 dissolution. *J. Biomed. Mater. Res.* **2001**, *55*, 151–157, doi: 10.1002/1097-4636(200105)55:2<151::AID-JBM1001>3.0.CO;2-D.
3. Day, R.M. Bioactive glass stimulates the secretion of angiogenic growth factors and angiogenesis in vitro. *Tissue Eng.* **2005**, *11*, 768–777, doi: 10.1089/ten.2005.11.768.
4. Allan, I.; Newman, H.; Wilson, M. Antibacterial activity of particulate Bioglass[®] against supra- and subgingival bacteria. *Biomaterials* **2001**, *22*, 1683–1687, doi: 10.1016/S0142-9612(00)00330-6.
5. Day, R.M.; Boccaccini, A.R. Effect of particulate bioactive glasses on human macrophages and monocytes in vitro. *J. Biomed. Mater. Res. A* **2005**, *73A*, 73–79, doi: 10.1002/jbm.a.30262.
6. Bockman, R.S.; Repo, M.A.; Warrell Jr., R.P.; Pounds, J.G.; Schidlovsky, G.; Gordon, B.M.; Jones, K.W. Distribution of trace levels of therapeutic gallium in bone as mapped by synchrotron X-ray microscopy. *Proc. Natl. Acad. Sci. USA* **1990**, *87*, 4149–4153.
7. Verron, E.; Loubat, A.; Carle, G.F.; Vignes-Colombeix, C.; Strazic, I.; Guicheux, J.; Rochet, N.; Bouler, J.M.; Scimeca, J.C. Molecular effects of gallium on osteoclastic differentiation of mouse and human monocytes. *Biochem. Pharmacol.* **2012**, *83*, 671–679, doi: 10.1016/j.bcp.2011.12.015.

8. Ma, Z.; Fu, Q. Therapeutic effect of organic gallium on ovariectomized osteopenic rats by decreased serum minerals and increased bone mineral content. *Biol. Trace Elem. Res.* **2010**, *133*, 342–349, doi: 10.1007/s12011-009-8445-3.
9. Bernstein, L.R. Mechanism of therapeutic activity for gallium. *Pharmacol. Rev.* **1998**, *50*, 665–682.
10. Bockman, R.S.; Bosco, B. Treatment of patients with advanced Paget's disease of bone with two cycles of gallium nitrate. *Semin. Arthritis Rheum.* **1994**, *23*, 268–269, doi: 10.1016/0049-0172(94)90057-4.
11. Campoccia, D.; Montanaro, L.; Arciola, C.R. The significance of infection related to orthopedic devices and issues of antibiotic resistance. *Biomaterials* **2006**, *27*, 2331–2339, doi: 10.1016/j.biomaterials.2005.11.044.
12. Kaneko, Y.; Thoendel, M.; Olakanmi, O.; Britigan, B.E.; Singh, P.K. The transition metal gallium disrupts *Pseudomonas aeruginosa* iron metabolism and has antimicrobial and antibiofilm activity. *J. Clin. Invest.* **2007**, *117*, 877–888, doi: 10.1172/JCI30783.
13. Chitambar, C.R.; Narasimhan, J. Targeting iron-dependent DNA synthesis with gallium and transferrin-gallium. *Pathobiology* **1991**, *59*, 3–10, doi: 10.1159/000163609.
14. Bullen, J.J.; Rogers, H.J.; Spalding, P.B.; Ward, C.G. Iron and infection: the heart of the matter. *FEMS. Immunol. Med. Microbiol.* **2005**, *43*, 325–330, doi: 10.1016/j.femsim.2004.11.010.
15. Cochis, A.; Azzimonti, B.; Della Valle, C.; De Giglio, E.; Bloise, N.; Visai, L.; Cometa, S.; Rimondini, L.; Chiesa, R. The effect of silver or gallium doped titanium against the multidrug resistant *Acinetobacter baumannii*. *Biomaterials* **2016**, *80*, 80–95, doi: 10.1016/j.biomaterials.2015.11.042.
16. Verron, E.; Masson, M.; Khoshniat, S.; Duplomb, L.; Wittrant, Y.; Baud'huin, M.; Badran, Z.; Bujoli, B.; Janvier, P.; Scimeca, J.-C. Bouler, J.-M.; Guicheux, J. Gallium modulates osteoclastic bone resorption in vitro without affecting osteoblasts. *Br. J. Pharmacol.* **2010**, *159*, 1681–1692, doi: 10.1111/j.1476-5381.2010.00665.x.
17. Salinas, A.J.; Shruti, S.; Malavasi, G.; Menabue, L.; Vallet-Regi, M. Substitutions of cerium, gallium and zinc in ordered mesoporous bioactive glasses. *Acta Biomater.* **2011**, *7*, 3452–3458, doi: 10.1016/j.actbio.2011.05.033.
18. Pourshahrestani, S.; Zeimaran, E.; Adib Kadri, N.; Gargiulo, N.; Mahmood Jindal, H.; Vasudevaraj Naveen S.; Devi Sekaran, S.; Kamarul, T.; Towler M.R. Potency and Cytotoxicity of a Novel Gallium-Containing Mesoporous Bioactive Glass/Chitosan Composite Scaffold as Hemostatic Agents. *ACS Appl. Mater. Interfaces* **2017**, *9*, 31381–31392, doi: 10.1021/acsami.7b07769.

19. Valappil, S.P.; Ready, D.; Abou Neel, E.A.; Pickup, D.M.; Chrzanowski, W.; O'Dell, L.A.; Newport, R.J.; Smith, M.E.; Wilson, M.; Knowles, J.C. Antimicrobial Gallium-Doped Phosphate-Based Glasses. *Adv. Funct. Mater.* **2008**, *8*, 732–741, doi: 10.1002/adfm.200700931.
20. Shruti, S.; Salinas, A.J.; Malavasi, G.; Lusvardi, G.; Menabue, L.; Ferrara, C.; Mustarelli, P.; Vallet-Regí, M. Structural and in vitro study of cerium, gallium and zinc containing sol-gel bioactive glasses. *J. Mater. Chem.* **2012**, *22*, 13698–13706, doi: 10.1039/C2JM31767B.
21. Malavasi, G.; Menabue, L.; Menziani, M.C.; Pedone, A.; Salinas, A.J.; Vallet-Regí, M. New insights into the bioactivity of SiO₂-CaO and SiO₂-CaO-P₂O₅ sol-gel glasses by molecular dynamics simulations. *J. Sol-Gel Sci. Technol.* **2013**, *67*, 208–219, doi: 10.1007/s10971-011-2453-4.
22. Sanchez-Salcedo, S.; Shruti, S.; Salinas, A.J.; Malavasi, G.; Menabue, L.; Vallet-Regí, M. In vitro antibacterial capacity and cytocompatibility of SiO₂-CaO-P₂O₅ meso-macroporous glass scaffolds enriched with ZnO. *J. Mater. Chem. B* **2014**, *2*, 4836–4847, doi: 10.1039/C4TB00403E.
23. Lopez-Noriega, A.; Arcos, D.; Izquierdo-Barba, I.; Sakamoto, Y.; Terasaki, O.; Vallet-Regí, M. Ordered mesoporous bioactive glasses for bone tissue regeneration. *Chem. Mater.* **2006**, *18*, 3137–3144, doi: 10.1021/cm060488o.
24. Hill, R.G.; Brauer, D.S. Predicting the bioactivity of glasses using the network connectivity or split network models. *J. Non-Cryst. Solids* **2011**, *357*, 3884–3887, doi: 10.1016/j.jnoncrysol.2011.07.025.
25. Martin, R.A.; Moss, R.M.; Lakhkar, N.J.; Knowles, J.C.; Cuello, G.J.; Smith, M.E.; Hanna, J.V.; Newport, R.J. Structural characterization of titanium-doped Bioglass using isotopic substitution neutron diffraction. *Phys. Chem. Chem. Phys.* **2012**, *14*, 15807–15815, doi: 10.1039/C2CP43032K.
26. Gunawidjaja, P.N.; Mathew, R.; Lo, A.Y.H.; Izquierdo-Barba, I.; Garcia, A.; Arcos, D.; Vallet-Regí, M.; Eden, M. Local structures of mesoporous bioactive glasses and their surface alterations *in vitro*: inferences from solid-state nuclear magnetic resonance. *Phil. Trans. R. Soc. A* **2012**, *370*, 1376–1399, doi: 10.1098/rsta.2011.0257.
27. Garcia, A.; Cicuendez, M.; Izquierdo-Barba, I.; Arcos, D.; Vallet-Regí, M. Essential Role of Calcium Phosphate Heterogeneities in 2D-Hexagonal and 3D-Cubic SiO₂-CaO-P₂O₅ Mesoporous Bioactive Glasses. *Chem. Mater.* **2009**, *21*, 5474–5484, doi: 10.1021/cm9022776.
28. Leonova, E.; Izquierdo-Barba, I.; Arcos, D.; Lopez-Noriega, A.; Hedin, N.; Vallet-Regí, M.; Eden, M. Multinuclear solid-state NMR studies of ordered mesoporous bioactive glasses. *J.*

- Phys. Chem. C* **2008**, *112*, 5552–5562, doi: 10.1021/jp7107973.
29. Kokubo, T.; Takadama, H. How useful is SBF in predicting in vivo bone bioactivity? *Biomaterials* **2006**, *27*, 2907–2915, doi: 10.1016/j.biomaterials.2006.01.017.
30. Martinez, A.; Izquierdo-Barba, I.; Vallet-Regi, M. Bioactivity of CaO–SiO₂ binary glass system. *Chem. Mater.* **2000**, *12*, 3080–3088, doi: 10.1021/cm001107o.
31. de Andrade, J.S.; Pintiero, A.G.; Vasconcelos, I.F.; Sasaki, J.M.; de Paiva, J.A.C.; Valente, M.A.; Sombra, A.S.B. Raman and infrared spectra of KNbO₃ in niobate glass-ceramics. *J. Phys. Condens. Matter* **1999**, *11*, 4451–4460, doi: 10.1088/0953-8984/11/22/315.
32. Vallet-Regi, M.; Izquierdo-Barba, I.; Salinas, A.J. Influence of P₂O₅ on crystallinity of apatite formed in vitro on surface of bioactive glass. *J. Biomed. Mater. Res. A* **1999**, *46*, 560–565, doi: 10.1002/(SICI)1097-4636(19990915)46:4<560::AID-JBM14>3.0.CO;2-M
33. Wren, A.W.; Jones, M.C.; Misture, S.T.; Coughlan, A.; Keenan, N.L.; Towler, M.R.; Hall, M.M. A preliminary investigation into the structure, solubility and biocompatibility of solgel SiO₂–CaO–Ga₂O₃ glass-ceramics. *Mater. Chem. Phys.* **2014**, *148*, 416–425, doi: 10.1016/j.matchemphys.2014.08.006.
34. Aina, V.; Morterra, C.; Lusvardi, G.; Malavasi, G.; Menabue, L.; Shruti, S.; Bianchi, C.L.; Bolis, V. Ga-Modified (Si–Ca–P) Sol-Gel Glasses: Possible Relationships between Surface Chemical Properties and Bioactivity. *J. Phys. Chem. C* **2011**, *115*, 22461–22474, doi: 10.1021/jp207217a.
35. Malavasi, G.; Pedone, A.; Menziani, M.C. Study of the Structural Role of Gallium and Aluminum in 45S5 Bioactive Glasses by Molecular Dynamics Simulations. *J. Phys. Chem. B* **2013**, *117*, 4142–4150, doi: 10.1021/jp400721g.
36. Otero Areán, C.; Turnes Palomino, G.; Geobaldo, F.; Zecchina, A. Characterization of Gallosilicate MFI-Type Zeolites by IR Spectroscopy of Adsorbed Probe Molecules. *J. Phys. Chem.* **1996**, *100*, 6678–6690, doi: 10.1021/jp952952a.
37. Turnes Palomino, G.; Cuart Pascual, J. J.; Rodriguez Delgado, M.; Parra, J. B.; Otero Areán, C. FT-IR studies on the acidity of gallium-substituted mesoporous MCM-41 silica. *Mater. Chem. Phys.* **2004**, *85*, 145–150, doi: 10.1016/j.matchemphys.2003.12.020.
38. Hadjiivanov, K.I.; Vayssilov G.N. Characterization of oxide surfaces and zeolites by carbon monoxide as an IR probe molecule. *Adv. Catal.* **2002**, *47*, 307–511, doi: 10.1016/S0360-0564(02)47008-3.
39. Ren, J.; Eckert, H. Intermediate Role of Gallium in Oxidic Glasses: Solid State NMR Structural Studies of the Ga₂O₃–NaPO₃ System. *J. Phys. Chem. C* **2014**, *18*, 15386–15409, doi: 10.1021/jp504023k.
40. Linati, L.; Lusvardi, G.; Malavasi, G.; Menabue, L.; Menziani, M.C.; Mustarelli, P.; Segre, U.

Qualitative and quantitative Structure-Property Relationships analysis of multicomponent potential bioglasses. *J. Phys. Chem. B* **2005**, *109*, 4989–4998, doi: 10.1021/jp046631n.

41. Lao, J.; Nedelec, J.M.; Moretto, Ph.; Jallot, E. Micro-PIXE–RBS methods highlighting the influence of phosphorus on the in vitro bioactivity of sol–gel derived glass particles in the SiO₂–CaO–P₂O₅ system. *Nucl. Instrum. Methods Phys. Res. B* **2008**, *266*, 2412–2417, doi: 10.1016/j.nimb.2008.03.013.
42. Minandri, F.; Bonchi, C.; Frangipani, E.; Imperi, F.; Visca, P. Promises and failures of gallium as an antibacterial agent. *Future Microbiol.* **2014**, *9*, 379–397, doi: 10.2217/fmb.14.3.
43. Brunauer, S.; Emmet, P.H.; Teller, E. Adsorption of gases in multimolecular layers. *J. Am. Chem. Soc.* **1938**, *60*, 309–319, doi: 10.1021/ja01269a023.
44. Barrett, E.P.; Joyner, L.G.; Halenda, P.P. The Determination of Pore Volume and Area Distributions in Porous Substances. I. Computations from Nitrogen Isotherms. *J. Am. Chem. Soc.* **1951**, *73*, 373–380, doi: 10.1021/ja01145a126.